

Superconducting properties of the 2D models with different types of inter-particle coupling

V.M. Loktev

*Bogolyubov Institute for Theoretical Physics,
Metrologicheskaya Str. 14-b, Kiev, 03143, Ukraine**

V. Turkowski[†]

CFIF, Instituto Superior Tecnico, Av.Rovisco Pais, 1049-001 Lisbon, Portugal

(Dated: April 7, 2003)

Abstract

The superconducting properties of the 2D fermion system with local and different types of the indirect boson-exchange attractions in the cases of s -wave and d -wave pairing are reviewed and analysed at $T = 0$. In particular, the possibility of the crossover from the Bose-Einstein condensation regime to the BCS-like superconductivity with the carrier density and coupling changing in the case of different pairing channels is discussed. Gaussian fluctuations of the order parameter are taken into account and the carrier density dependence of the gap is studied in this case. The role of the interaction form in the physical behavior of the systems is also discussed.

PACS numbers: 74.20Rp, 74.25Dw, 74.62.Dh, 74.72.-h

*Electronic address: vloktev@bitp.kiev.ua

[†]Electronic address: vturk@cfif.ist.utl.pt

I. INTRODUCTION

The theoretical description of the carrier density dependence of the physical properties of superconductors has a long history. Probably, the first attempt to solve this problem self-consistently was made by Eagles in Ref. [1], where the author tried to apply his results for description of the superconducting properties of *Zr*-doped *SrTiO*₃ [2]. The author studied the dependence of the superconducting gap at $T = 0$ and of the mean-field critical temperature on charge carrier density in the two-dimensional (2D) and in the three-dimensional (3D) systems with phonon-like attraction at low carrier densities. The set of the equations for the superconducting gap and Fermi energy in two and three dimensions was analyzed. It was estimated that the diameter of pairs is smaller than distance between pairs at low carrier densities, therefore, superconductivity at low carrier densities transforms into superfluidity of small (local) pairs. Now this phenomena is known as crossover from superfluidity to superconductivity with carrier density changing. It was also shown by Eagles that there exists a critical value of the inter-particle coupling below which there is no local pairs at low carrier densities in the 3D system. It is worth to mention that the possibility of superfluidity scenario of superconductivity was also proposed by Ogg [3] and Schafroth [4, 5, 6] before paper [1].

Later the problem of the crossover was studied by Leggett in [7], where the author studied 3D system with short-range repulsion and finite-range attraction. He analyzed the properties of the system changing dimensionless parameter $1/(ak_F)$, where a is the scattering length and k_F is the Fermi momentum which defines the particle number in the system. It was shown that in the limiting cases the system consists of bound “diatomic molecules” at $1/(ak_F) = \infty$, and the Cooper pairing takes place at $1/(ak_F) = -\infty$.

Nozières and Schmitt-Rink [8] generalized the results of Leggett on the cases of finite temperatures and lattice model when the interaction potential is separable. They have shown that the crossover from superfluidity to superconductivity is smooth with k_F and interaction (attraction) potential V changing, when V is larger than the critical value for two-particle bound state formation. All the results mentioned above correspond to the case of the *s*-wave pairing.

The real boom in the interest to the crossover phenomena has started in the second half of eighties after the discovery of high-temperature superconductors (HTSCs), materials with

very unusual dependence of superconducting properties on the carrier density.

Theory of the HTSC still remains one of the most difficult and one of the most important problems of the modern condensed matter theory. Due to complicated crystal structure, anisotropic pairing, strong electron correlations, presence of the disorder, low dimensionality of this materials and some other complications, the construction of the self-consistent theory of HTSCs is not completed so far.

During the last years many models which take into account some of the cuprate properties were proposed for describing the doping and interaction dependence of the superconducting gap and of the superconducting critical temperature.

The 3D crossover from superfluidity to superconductivity in the s -wave pairing channel for the model with local attraction was studied in [9, 10, 11, 12, 13, 14, 15, 16] for the model with local (so called 4F-) attraction, and in [17] for the case of separable potential. In [9] the additional case with local repulsion and inter-site attraction was considered. The role of the order parameter fluctuations at $T = 0$ was analyzed in [18] (3D case) and in [19] (2D and 3D cases). The quasi-2D model with s -wave pairing at $T = 0$ was considered in [20].

For the 2D case the problem of the crossover in the s -wave pairing channel was analyzed at zero temperature (when a long-range superconducting order is still possible in a 2D system [21]) in [9, 12, 15, 17, 22, 23, 24, 25, 26, 27], and at finite temperatures in [9, 12, 15, 16, 17, 24, 25, 26, 28, 29]. The metal-superconductor phases boundaries on the $n - U$ phase diagram of the 2D attractive Hubbard model at $T = 0$ was studied in [30] by means of the Dynamical Mean-Field Theory. The crossover problem for the 2D phonon-mediated model in the s -wave channel at $T=0$ was studied in [31, 32].

The 2D d -wave crossover for models with separable potential was studied in [15, 28, 33] at $T = 0$. The Ginzburg-Landau potential with carrier density dependent parameters for the 2D d -wave superconductor at finite T was considered in [34]. The doping dependence of the critical temperature in the strongly correlated electron model with the electron-phonon coupling was studied in [35, 36]. It was shown that the vertex correction to the electron-phonon interaction in this model leads to the increasing of superconductivity in the d -wave pairing channel. In paper [25] the cases with different pairing symmetries s , s_{xy} , d_{xy} and $d_{x^2-y^2}$ in the 2D system with local, nearest neighbor, and next nearest neighbor attraction were studied at $T = 0$ and finite T in order to describe the doping dependence of the zero superconducting gap and superconducting critical temperature. The possibility of zero

temperature s -, d - and mixed $s + id$ pairing in the 2D system as function of coupling were studied in paper [37]. The same problem in the quasi-2D Hubbard model with nearest neighbor attraction at finite temperature was studied in [39], where also doping dependence of the superconducting properties was considered.

The 2D model with the nearest neighbor (n.n.) attraction and next nearest neighbor (n.n.n.) hopping at $T = 0$ was considered in [40]. It was shown that at some relation between n.n. and n.n.n. hopping the system is always in Bose-Einstein condensation regime and that there is no pairing at low carrier density when coupling is weak (see also [33]). However, as it was shown in [41] this statement is not correct. The 2D model with local repulsion and n.n. attraction at $T = 0$ in the s -wave and d -wave channels was studied in [42]. The role of the n.n.n. hopping was analyzed. The s -wave and d -wave pairing crossover at $T = 0$ in the model with doping dependent attraction was considered in [43]. It is interesting to mention that the boson-fermion model with electron and hole sectors and different kinds of fermion-boson coupling was proposed in [44] to unify the BEC and BCS phenomena. Superconductivity or superfluidity regimes take place at different model parameters.

Despite the d -wave pairing symmetry is considered as a typical property of cuprates [45], there are experimental evidences that the s -wave or mixed $s + d$ pairings take place in some materials at certain values of doping. Thus, it was shown that optimally doped $Pr_{1.855}Ce_{0.145}CuO_{4-y}$ at low temperatures demonstrates nodeless gap inconsistent with d -wave pairing [46], and electron doped superconductor $Sr_{0.9}La_{0.1}CuO_2$ demonstrate s -wave pairing near optimal doping [47]. The analysis by Zhao [48] shows that dominant bulk symmetry of the order parameter in some cuprates is extended or anisotropic s -wave symmetry. It was also found that the crossover from d -wave pairing in underdoped and optimally doped regime to $s+d$ -wave pairing in overdoped regime takes place in $YBa_2Cu_3O_{7-\delta}$ [49]. Crossover from d -wave pairing to s -wave pairing with doping near optimal c was found for electron doped $Pr_{2-x}Ce_xCuO_4$ [50] and for $Pr_{2-x}Ce_xCuO_{4-y}$, $La_{2-x}Ce_xCuO_{4-y}$ [51]. However, the s -wave pairing is not always present in overdoped cuprates, d -wave regime in overdoped $Tl_2Ba_2Cu_3O_{6+\delta}$ was found in [52].

Below we analyze the behavior of the superconducting systems with different inter-particle potentials in the s -wave and d -wave pairing channels at $T = 0$ as functions of particle density and interaction strength. We shortly review the main properties of different systems. We apologize for these authors whose results are not presented here, since it is very difficult to

cover all the results in such wide and fastly growing field as theory of superconductivity, even in a case of some special topic.

II. THE MAIN EQUATIONS

The most general Hamiltonians, which is usually studied in theory of superconductivity can be written as:

$$H = - \sum_{n,m,\sigma} t_{nm} c_{n\sigma}^\dagger c_{m\sigma} - \mu \sum_{n,\sigma} c_{n\sigma}^\dagger c_{n\sigma} - V_0 \sum_n c_{n\uparrow}^\dagger c_{n\downarrow}^\dagger c_{n\downarrow} c_{n\uparrow} - \sum_{n,m} V_{nm} c_{n\uparrow}^\dagger c_{m\downarrow}^\dagger c_{m\downarrow} c_{n\uparrow} + \sum_{n,q} g_n(q) c_{n\sigma}^\dagger c_{n\sigma} \vec{X}_n(q) + \frac{1}{2} \sum_{n,q} \left[\frac{\vec{p}_n^2(q)}{m(q)} + m(q) \omega_n^2(q) \vec{X}_n^2(q) \right], \quad (1)$$

where $c_{n\sigma} \equiv c_\sigma(\tau, n)$ is a fermionic field operator with spin $\sigma = \uparrow, \downarrow$ at lattice site n and at time τ , t_{ij} describes the nearest neighbor (n.n.), next nearest neighbor (n.n.n.) and other hopping processes; μ is the chemical potential of the system. The inter-particle interaction is described by the terms proportional to V_0 (local interaction) and V_{nm} (n.n. or n.n.n. interaction). The last two terms describe additional electron boson interaction and free boson parts of the Hamiltonian, where q is a boson mode with coordinate $\vec{X}_n(q)$, momentum $\vec{p}_n(q)$ and frequency $\omega_n(q)$ and $g_n(q)$ is the fermion-boson coupling. One can easily pass to the continuum version of this Hamiltonian with substitution of the n.n. hopping operator t_{nm} by $t_{nm} \rightarrow \delta_{nm} t (1 - (a^2/(2d)) \nabla^2)$ (where a is the inter-cite distance, d is the dimensionality of the system), introducing radius cut off in the the interaction terms, etc.

In the case of the d-dimensional square lattice the free fermion dispersion relation in the momentum space has the following form, when the n.n. hopping takes place

$$\xi(\mathbf{k}) = -2t \sum_{j=1}^d \cos(ak_j) - \mu, \quad (2)$$

where $\mathbf{k}$ is a d-dimensional wave vector.

It is convenient to find the thermodynamic potential by using the path integral approach for studying the properties of a quantum many-particle system. This method is not necessary in the case of the mean-field solution, but it is extremely useful when the fluctuations are studied.

The partition function of the system is

$$Z = \int D\psi^\dagger D\psi e^{-S} \quad (3)$$

with the action

$$S = \int_0^\beta d\tau \left[\sum_{n,\sigma} \psi_{n\sigma}^\dagger(\tau) \partial_\tau \psi_{n\sigma}(\tau) + H(\tau) \right]. \quad (4)$$

To study the superconducting properties of the system, we make the Hubbard-Stratonovich transformation with bilocal fields $\phi_{nm}(\tau_1, \tau_2)$ and $\phi_{nm}^\dagger(\tau_1, \tau_2)$ can be applied [53]:

$$\begin{aligned} & \exp \left[\psi_{n\uparrow}^\dagger(\tau_1) \psi_{m\downarrow}^\dagger(\tau_2) V_{nm}(\tau_1, \tau_2) \psi_{m\downarrow}(\tau_2) \psi_{n\uparrow}(\tau_1) \right] \\ &= \int D\phi^\dagger D\phi \exp \left[- \int_0^\beta d\tau_1 \int_0^\beta d\tau_2 \left(\frac{|\phi_{nm}(\tau_1, \tau_2)|^2}{V_{nm}(\tau_1, \tau_2)} \right. \right. \\ & \quad \left. \left. - \phi_{nm}^\dagger(\tau_1, \tau_2) \psi_{n\downarrow}(\tau_1) \psi_{m\uparrow}(\tau_2) - \psi_{n\uparrow}^\dagger(\tau_1) \psi_{m\downarrow}^\dagger(\tau_2) \phi_{nm}(\tau_1, \tau_2) \right) \right], \end{aligned} \quad (5)$$

where $V_{nm}(\tau_1, \tau_2)$ includes the effective inter-particle attraction due to boson coupling after intergrations over the field X .

Let us introduce the Nambu spinor

$$\Psi_n(\tau) = \begin{pmatrix} \psi_{n\uparrow}(\tau) \\ \psi_{n\downarrow}^\dagger(\tau) \end{pmatrix}, \quad \Psi_n^\dagger(\tau) = \left(\psi_{n\uparrow}^\dagger(\tau), \psi_{n\downarrow}(\tau) \right).$$

In this case the partition function can be written as

$$Z = \int D\psi^\dagger D\psi D\phi^\dagger D\phi e^{-S(\psi^\dagger, \psi, \phi^\dagger, \phi)}, \quad (6)$$

where

$$\begin{aligned} & S(\psi^\dagger, \psi, \phi^\dagger, \phi) \\ &= \int_0^\beta d\tau_1 \int_0^\beta d\tau_2 \sum_{n,m} \left\{ \frac{|\phi_{nm}(\tau_1, \tau_2)|^2}{V_{nm}(\tau_1, \tau_2)} - \delta(\tau_1 - \tau_2) \Psi_n^\dagger(\tau_1) [-\delta_{nm} \partial_{\tau_2} - \hat{\tau}_z(t_{nm} - \delta_{nm}\mu)] \Psi_m(\tau_2) \right. \\ & \quad \left. - \phi_{nm}^\dagger(\tau_1, \tau_2) \Psi_n^\dagger(\tau_1) \hat{\tau}_- \Psi_m(\tau_2) - \Psi_n^\dagger(\tau_1) \hat{\tau}_+ \Psi_m(\tau_2) \phi_{nm}(\tau_1, \tau_2) \right\} \end{aligned} \quad (7)$$

where $\hat{\tau}_\pm = \frac{1}{2}(\hat{\tau}_x \pm \hat{\tau}_y)$ are the Pauli matrices.

The last action is diagonal on fermionic fields, therefore the integration over $\Psi^\dagger$ and Ψ can be performed exactly. The partition function becomes in this case

$$Z = \int \mathcal{D}\phi \mathcal{D}\phi^* \exp(-\beta \Omega[\mathcal{G}]), \quad (\beta = 1/T)$$

where $\Omega[\mathcal{G}]$ is the thermodynamic potential, which in the "leading order" is

$$\beta\Omega[\mathcal{G}] = \int_0^\beta d\tau_1 \int_0^\beta d\tau_2 \sum_{n,m} \frac{|\phi_{nm}(\tau_1, \tau_2)|^2}{V_{nm}(\tau_1, \tau_2)} - \text{Tr} \text{Ln} G^{-1} + \text{Tr} \text{Ln} G_0^{-1}. \quad (8)$$

The Nambu spinor Green function G satisfies the following equation

$$\begin{aligned} \left[-\delta(\tau_1 - \tau_3) \partial_{\tau_3} \hat{I} + \delta(\tau_1 - \tau_3) (t_{nm} - \delta_{nl}\mu) \hat{\tau}_z + \hat{\tau}_+ \Phi_{nl}(\tau_1, \tau_3) + \hat{\tau}_- \Phi_{nl}^*(\tau_1, \tau_3) \right] G_{lm}(\tau_3, \tau_2) \\ = \delta(\tau_1 - \tau_2) \delta_{nm} \end{aligned}$$

with anti-periodic boundary conditions

$$G_{nm}(\tau_1 - \tau_2 + \beta) = -G_{nm}(\tau_1 - \tau_2).$$

The thermodynamic potential (8) is the most general form of the superconducting effective potential with non-local retarded inter-particle interaction. It will be used below to study the fluctuation effects.

The minimization of the thermodynamic potential with respect to the order parameter and chemical potential leads to the following system of the coupled equations for $\Phi_{nm}(\tau_n, \tau_m)$ and μ :

$$\frac{\delta\Omega}{\delta\Phi_{nm}(\tau_n, \tau_m)} = 0 \quad (9)$$

$$\frac{\partial\Omega}{\partial\mu} = -N_f, \quad (10)$$

or

$$\Phi_{nm}(\tau_1, \tau_2) = V_{nl}(\tau_1, \tau_3) \text{tr} \hat{\tau}_+ G_{lm}(\tau_3, \tau_2) \quad (11)$$

$$n_f = -\text{tr} \hat{\tau}_z G_{nn}(\tau_1, \tau_1^+), \quad (12)$$

where $n_f = N_f/v$ is particle density in the system (v is the volume of the system).

In general it is very difficult to find the Greens function $G_{nm}(\tau_1, \tau_2)$, therefore some simplifications must be applied. We shall consider the case of the space and time invariance, $V_{nm}(\tau_1, \tau_2) = V_{n-m,0}(\tau_1 - \tau_2)$. In this case the Green's function has the following form in the momentum space:

$$G(i\omega_n, \mathbf{k}) = -\frac{i\omega_n + \hat{\tau}_3 \xi(\mathbf{k}) - \Phi(i\omega_n, \mathbf{k}) \hat{\tau}_+ - \Phi^*(i\omega_n, \mathbf{k}) \hat{\tau}_-}{\omega_n^2 + \xi^2(\mathbf{k}) + |\Phi(i\omega_n, \mathbf{k})|^2},$$

and the system of the equations (11), (12) has the following form:

$$\begin{aligned} \Phi(i\omega_n, \mathbf{k}) &= \int \frac{d^d p}{(2\pi)^d} \sum_m \frac{\Phi(\omega_m, \mathbf{p})}{\omega_m^2 - \xi(\mathbf{p})^2 - |\Phi(\omega_m, \mathbf{p})|^2} \\ &\times \left[V(\mathbf{p}, \mathbf{k}) + g_b^2 \int \frac{d^d k}{(2\pi)^d} \frac{\omega(\mathbf{p} - \mathbf{k})^2}{-(\omega_m - \omega_n)^2 - \omega(\mathbf{p} - \mathbf{k})^2} \right] \end{aligned} \quad (13)$$

$$n_f = \int \frac{d^d p}{(2\pi)^d} \left[1 - \sum_m \frac{\xi(\mathbf{p})}{-\omega_m^2 - \xi(\mathbf{p})^2 - |\Phi(\omega_m, \mathbf{p})|^2} \right], \quad (14)$$

$V(\mathbf{p} - \mathbf{k})$ is the Fourier transform of the non-retarded interaction and the term proportional to g_b describes the inter-particle boson coupling, $\omega_n = \pi T(2n + 1)$ is the standard Matsubara frequency. Interaction term in (13) is written in general form. it describes, for example local non-retarded interaction, when $V(\mathbf{p} - \mathbf{k}) = \text{const}$, $g_b = 0$, non-local non-retarded interaction, when $V(\mathbf{p} - \mathbf{k}) \neq \text{const}$, $g_b = 0$, local retarded interaction, when $V(\mathbf{p} - \mathbf{k}) = \text{const}$, $g_b \neq 0$, $\omega(\mathbf{p} - \mathbf{k}) = \text{const}$ etc. The system (13), (14) will be analyzed in the next Section for different forms of the inter-particle potential $V(\mathbf{p}, \mathbf{k})$ and spectra $\omega(\mathbf{p} - \mathbf{k})$.

III. SOLUTIONS

A. Model with local non-retarded attraction

The problem of the crossover from small to large fermion density in the model with local attraction was considered in [1, 9, 10, 11, 12, 13, 14, 15, 16] for the 3D case and in [1, 9, 15, 22, 27] for the 2D case.

For the simplest case of local non-retarded attraction the interaction parameters in equations (13), (14) have the following form: $V(\mathbf{p}, \mathbf{k}) \equiv V = \text{const}$, $g_b = 0$. Therefore, the gap in this case is momentum and frequency independent

$$\Phi(\omega_n, \mathbf{k}) = \Delta = \text{const}.$$

The summation over frequency in (13), (14) can be easily performed, and one gets the standard system of the equations:

$$1 = V \int \frac{d^d k}{(2\pi)^d} \frac{1}{2\sqrt{\xi(\mathbf{k})^2 + \Delta^2}} \tanh \left(\frac{\sqrt{\xi(\mathbf{k})^2 + \Delta^2}}{2T} \right), \quad (15)$$

$$n_f = \int \frac{d^d k}{(2\pi)^d} \left[1 - \frac{\xi(\mathbf{k})}{\sqrt{\xi(\mathbf{k})^2 + \Delta^2}} \tanh \left(\frac{\sqrt{\xi(\mathbf{k})^2 + \Delta^2}}{2T} \right) \right], \quad (16)$$

which have a simple form at $T = 0$:

$$1 = V \int \frac{d^d k}{(2\pi)^d} \frac{1}{2\sqrt{\xi(\mathbf{k})^2 + \Delta^2}} \quad (17)$$

$$n_f = \int \frac{d^d k}{(2\pi)^d} \left[1 - \frac{\xi(\mathbf{k})}{\sqrt{\xi(\mathbf{k})^2 + \Delta^2}} \right]. \quad (18)$$

Since the gap is momentum independent, the only isotropic s -wave pairing regime is possible in the model with local attraction.

The s -wave pairing regime in the case of quadratic dispersion law

$$\xi(\mathbf{k}) = \frac{\mathbf{k}^2}{2m} - \mu$$

and indirect pairing with boson energy cut-off $\theta(|\xi(\mathbf{p}) - \mu| - \omega_c)$ was considered in the 2D and 3D case for low carrier densities by Eagles [1]. In fact, in this case the integration over momentum $\int d^d k / (2\pi)^d$ can be replaced by integration over energy $\int \rho(\epsilon) d\epsilon$, where $\rho(\epsilon)$ is the density of states (DOS), it is constant in the 2D case and $\sim \sqrt{\epsilon}$ in the 3D case.

It is very easy to solve system (17) and (18) in the 2D case. In the case when $\epsilon_F \ll W$ (W is a free fermion bandwidth) the solution has a simple form:

$$\Delta \simeq \sqrt{2W\epsilon_F} e^{-2\pi/(mV)},$$

$$\mu \simeq \epsilon_F - \frac{|\varepsilon_b|}{2},$$

where $\varepsilon_b = -2W e^{-4\pi/(mV)}$ is the two-particle bound state energy. Obviously, the crossover from superfluidity to superconductivity with doping takes place at any coupling constant, there exists the value of ϵ_F when $\mu = 0$ for any V .

This is not true in the 3D case, when the crossover takes place only when the coupling constant is larger than some critical value V_c . This difference follows from the difference in the DOS in the gap equation. In the 2D case $\rho(\epsilon) = \text{const}$ and the gap equation has the solution $\Delta = \sqrt{2W|\varepsilon_b|}$ at $\mu = 0$ and any coupling constant.

In the 3D case the gap equation has the following form

$$1 = V \int \frac{k^2 dk}{2\pi^2} \frac{1}{2\sqrt{k^4 + \Delta^2}} \quad (19)$$

at $\mu = 0$. The integral over k on the right hand side has maximal value $\sqrt{2mW}/(4\pi^2)$ at $\Delta = 0$. Therefore, a simple estimation for V_c is given by the relation $1 \simeq V_c \sqrt{2mW}/(4\pi^2)$, or $V_c \simeq 4\pi^2/\sqrt{2mW}$.

In the case of the momentum cut-off $\int \frac{d^d k}{(2\pi)^d} \theta(|\xi(\mathbf{p}) - \mu| - \omega_c)$ the approximate solution can be also easily obtained in the 2D case:

$$\Delta \simeq \sqrt{2|\varepsilon_b| \Delta_{BCS}} \theta(\omega_c - \epsilon_F) + \Delta_{BCS} \theta(\epsilon_F - \omega_c)$$

$$\mu = \epsilon_F - \frac{|\varepsilon_b|}{2},$$

where $\Delta_{BCS} = 2\omega_c e^{-2\pi/(mV)}$ is the BCS expression for the gap and the bound state energy in this case is $\varepsilon_b = -2\omega_c e^{-4\pi/(mV)}$. The gap is growing with doping in this case, and asymptotically reaches its maximal value $\Delta = \Delta_{BCS}$ when $\epsilon_F \gg \omega_c$.

In the 3D case the DOS in equations (17) and (18) can be substituted by the DOS on the Fermi level, and the 3D solution can be obtained from the 2D one with substitution $mV/(2\pi) \rightarrow k_F mV/(4\pi^2)$. It is possible to estimate the critical value of the coupling constant when the crossover takes place: $V_c = 2\pi^2/\sqrt{m\omega_c}$. In both cases with and without momentum cut off the transition from superfluidity to superconductivity is smooth, in other words the gap is growing with doping continuously.

B. Models with non-local non-retarded interaction

It is important to study a more realistic case of the non-local attraction in presence of the short range Coulomb repulsion. In order to study the superconducting properties of such a model in the channels with different pair angular momentum l , it is convenient (see [28, 29, 43], for example), to approximate the interaction potential by a separable function:

$$V_l(\mathbf{k}_1, \mathbf{k}_2) = -\lambda_l w_l(\mathbf{k}_1) w_l(\mathbf{k}_2), \quad (20)$$

where λ_l is an effective coupling constant, and

$$w_l(\mathbf{k}) = h_l(k) \cos(l\varphi_{\mathbf{k}}), \quad (21)$$

$$h_l(k) = \frac{(k/k_1)^l}{(1 + k/k_0)^{l+1/2}}, \quad (22)$$

k is the momentum modulus $k = |\mathbf{k}|$ and $\varphi_{\mathbf{k}}$ is the momentum angle in polar coordinates $\mathbf{k} = k(\cos(\varphi_{\mathbf{k}}), \sin(\varphi_{\mathbf{k}}))$. Parameters k_0 and k_1 put the momentum range in the proper region - the potential is attractive at $r_0 < r < r_1$ and repulsive at $r < r_0$, where $k_0 \sim 1/r_0$ and $k_1 \sim 1/r_1$.

It is easy to see that the interaction potential (20) has the correct asymptotic behavior at small and large momenta: $V_l(\mathbf{k}_1\mathbf{k}_2) \sim k_1^l k_2^l$ and $V_l(\mathbf{k}_1\mathbf{k}_2) \sim 1/\sqrt{k_1 k_2}$, correspondingly. Since the region of low carrier concentrations, where the crossover can take place, is the most interesting, the correct behavior of the interaction potential at small momenta is the most important. The small momenta give the main contribution to the integrals in the case of low carrier concentrations (see equations below). We shall study s - and d -wave channels with $l = 0$ and 2 separately, so we assume that the parameters λ_l for both channels are independent.

In this case the equations for the gap and for the chemical potential have the following form:

$$\Delta_l(\mathbf{k}) = -\lambda_l \int \frac{d\mathbf{p}}{(2\pi)^2} \frac{\Delta_l(\mathbf{p})}{2\sqrt{\varepsilon^2(\mathbf{p}) + \Delta_l(\mathbf{p})^2}} V_l(\mathbf{p}, \mathbf{k}), \quad (23)$$

$$\int \frac{d\mathbf{p}}{(2\pi)^2} \left[1 - \frac{\varepsilon(\mathbf{p})}{\sqrt{\varepsilon^2(\mathbf{p}) + \Delta_l(\mathbf{p})^2}} \right] = n_f. \quad (24)$$

The solution of equation (23) has the following form

$$\Delta_l(\mathbf{k}) = \Delta_l^{(0)} w_l(\mathbf{k}), \quad (25)$$

where $\Delta_l^{(0)}$ does not depend on the momentum $\mathbf{k}$.

As it was shown in [28, 29], the crossover from superfluidity to superconductivity is smooth with doping increasing (see Figs. 1 and 2 below). However, there exists a critical value of the interaction potential in the d -wave pairing channel, below which the crossover from superconductivity to superfluidity is impossible in the d -wave pairing channel.

The more realistic case in connection to HTSCs was considered in [43], where the correlation length r_0 was considered at small carrier densities as $r_0 \sim a/\sqrt{n_f}$. This dependence for the length of spin-spin correlations at small carrier densities was found for example in $La_{2-x}Sr_xCuO_4$. The magnetic correlation length decreases with carrier density per cell in this material as $3.8\text{\AA}/\sqrt{n_f}$ [54]. The value of a was considered to be $a = \sqrt{2/\pi}a_0$, a_0 is the square lattice constant. The following equality gives the value for a : $(\pi/2)r_0^2 N_f = a_0^2 N_{cell}$,

where on the left side the volume of the 2D system is expressed as a volume (circle of the radius $\sim r_0$) occupied by one particle, multiplied by the full number of particles N_f , N_{cell} is an elementary cell number in the system. The free fermion bandwidth W is connected with a_0 as $W = \pi^2/(ma_0^2)$. It should be noted, that the relation $r_0 \sim a/\sqrt{n_f}$ at $a = \sqrt{2/\pi}a_0$ is in a good agreement with the experimental data for $La_{2-x}Sr_xCuO_4$ [54], where the plane magnetically ordered lattice parameters are equal to 5.354 Å and 5.401 Å, and the corresponding parameter a is $\simeq 3.8$ Å.

It was shown the the critical value of the coupling exists even in the s -wave pairing channel for this case (see Figs.1 and 2).

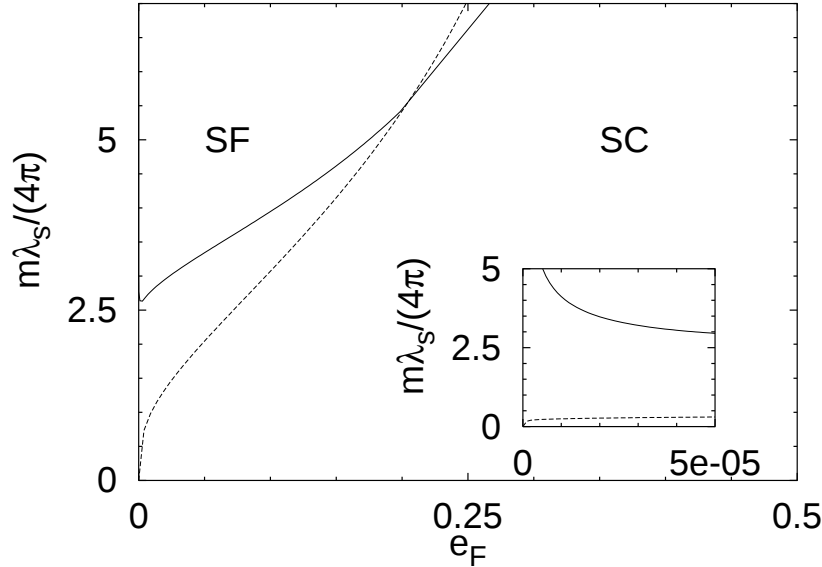


FIG. 1: Crossover line coupling-carrier density is presented for the s -pairing channel (solid line). The dotted line represents the corresponding curve for the case $r_0(n_f) = const$ at $r_0 = a_0$. The insert shows the doping dependence of the crossover value for coupling at very low charge carrier densities [43]. Here and below all parameters are expressed in units of the bandwidth W

Different versions of the previous model can be considered. Namely, the correlation radius $r_0(n_f) = a_0\sqrt{2/(\pi n_f)}$ can be introduced in a model with exponential decay of the attraction:

$$V_b(r, t) = g_{e-b} \frac{e^{-r/r_0}}{r} \quad (26)$$

Its Fourier transform has the following form:

$$D_b(\mathbf{q}) = \frac{g_{e-b}r_0}{(2\pi)^2\sqrt{1+r_0^2\mathbf{q}^2}}. \quad (27)$$

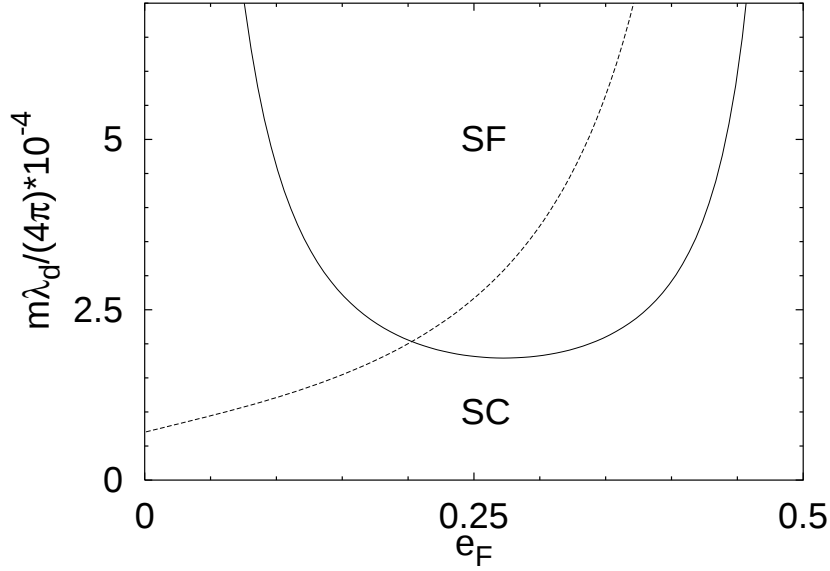


FIG. 2: The crossover line coupling-carrier density is presented for the d -wave case (solid line). The dotted line is the crossover curve for the case $r_0(n_f) = \text{const}$ at $r_0 = a_0$ [43].

In addition, the same kind of the short-range repulsion can be introduced in the model. It is easy to see, that in the 2D case this potential has the following form (see, for example [55]):

$$D_e(\mathbf{q}) = \frac{g_{e-e}}{q + q_{TF}g(q/2k_F)}, \quad (28)$$

where $g_{e-e} \equiv 2\pi e^2$, the Thomas-Fermi momentum is $q_{TF} = 4e^2m/\pi = 4/\pi a_B$, and $a_B = 1/(e^2m) \simeq 0.529 \text{ \AA}$ is the Bohr radius. The function $g(x)$ is defined as

$$g(x) = 1 - \theta(x - 1)\sqrt{1 - 1/x^2}. \quad (29)$$

This model in the s -wave pairing channel demonstrates the crossover from superfluidity to superconductivity at any value of the coupling constant, contrary to the previous case, see Fig.3. The doping dependence of the gap and of the chemical potential at different values of the dimensionless interaction parameters $\lambda_{e-b} = g_{e-b}^2 m r_0 / (8\pi^2)$, $\lambda_{e-e} = g_{e-e}^2 m r_0 / (4\pi)$ is presented in Figs. 4 and 5. As it follows from these Figures, the gap is decreasing with doping growing. This situation is in a qualitative agreement with the experiments for the cuprates. One can consider also an interesting situation of the combined local+non-local attraction, when the local attraction will tend the Cooper pairs to transform into the local pairs.

The “mixed” case with $h_l(k) = 1$ and $\lambda = \lambda_s + \lambda_d \cos(2\phi_{\mathbf{k}})$ was considered in Ref.

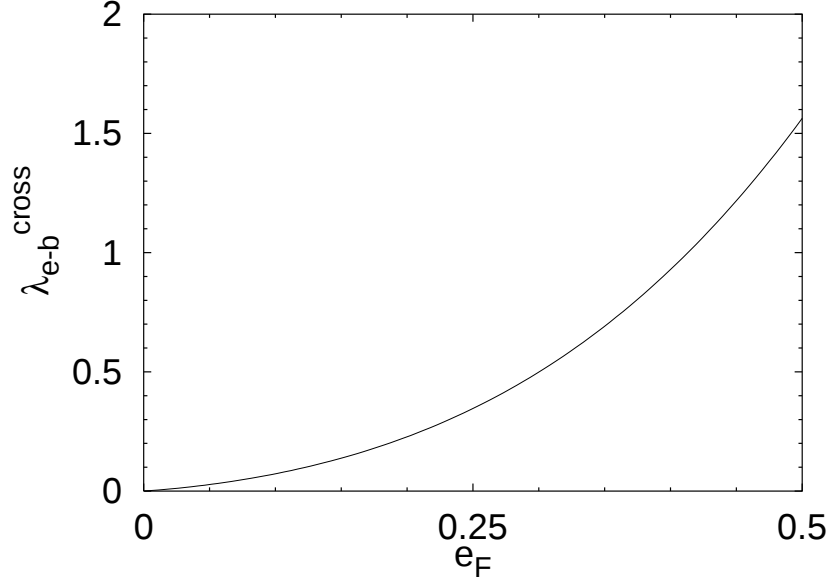


FIG. 3: The crossover interaction value λ_{e-b}^{cross} (defined by the condition $\mu = 0$) is presented as a function of ϵ_F at $\lambda_{e-e} = 0$.

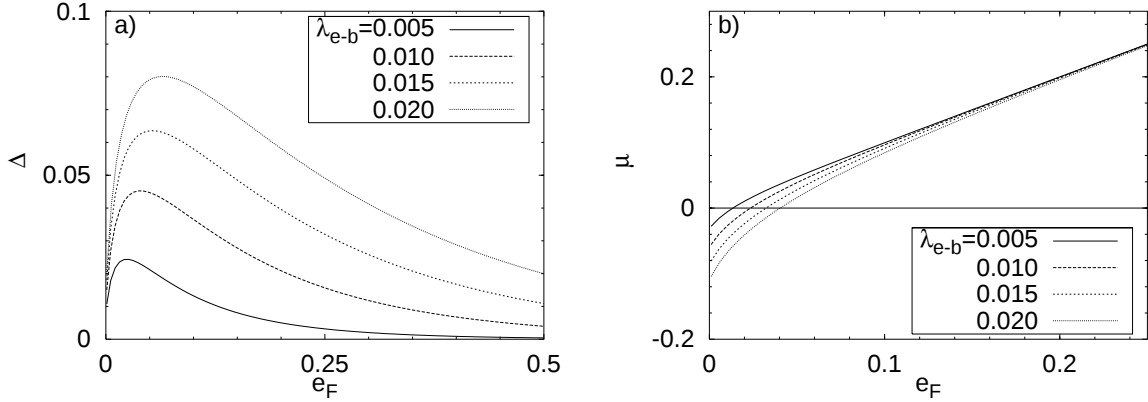


FIG. 4: The gap (a) and the chemical potential (b) as functions of ϵ_F at different λ_{e-b} and $\lambda_{e-e} = 0$.

[37, 38]. In particular, it was shown in [37] that the crossover from the d -wave to the s -wave superconductivity with the intermediate $s + d$ -phase takes place with doping in agreement with the experiments on some cuprate materials [49, 50, 51].

The d -wave case $w_d(\mathbf{k}) = \cos(k_x) - \cos(k_y)$ was considered in [33, 40, 41]. In particular, the role of the next nearest neighbor hopping t' on the pairing was studied in [40, 41]. As it was shown in [41], the crossover with doping take place at any value of t' , when the coupling constant is bigger than V_c .

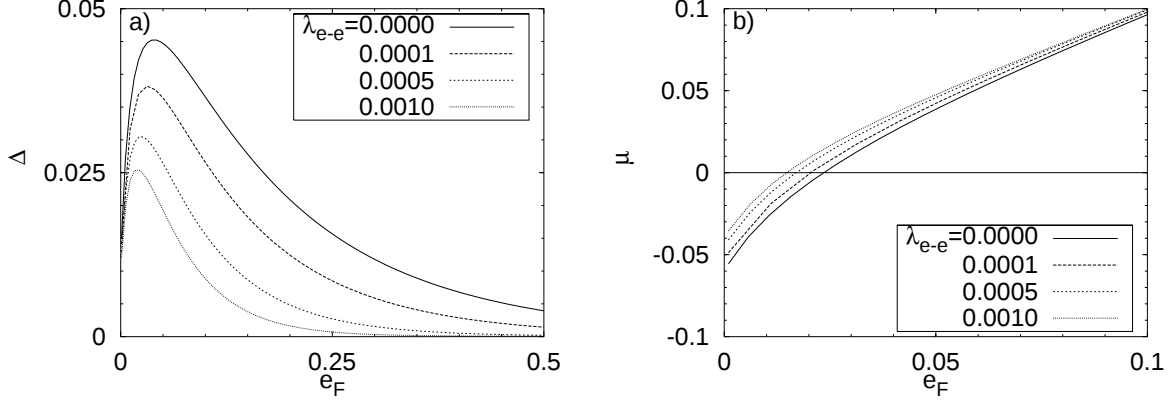


FIG. 5: The gap (a) and the chemical potential (b) as functions of ϵ_F at different λ_{e-e} and $\lambda_{e-b} = 0.01$.

It was stated in [25], that the model with small on-site repulsion and nearest neighbor V_1 and next nearest neighbor V_2 attraction with $V_2 \sim 60 - 80\text{meV}$ and $V_2/V_1 \simeq 1.3 - 1.5$ can describe the experimental data for hole-doped oxides.

C. Models with retarded interaction

The retardation effects in the interaction can play very important role the superconducting properties of the system. Let us consider a boson propagator with the dispersion $\omega = \omega(\mathbf{k})$:

$$D(\omega, \mathbf{k}) = \frac{\omega^2(\mathbf{k})}{\omega^2 - \omega^2(\mathbf{k}) + i\delta}, \quad (30)$$

where the spectra $\omega(\mathbf{k})$. For example, in the general case of phonon dispersion one has $\omega(\mathbf{k}) = \sqrt{\omega_0^2 + c^2\mathbf{k}^2}$. We shall study this rather general case below with the following approximation: $D(\omega, \mathbf{k}) \simeq D(\omega, \mathbf{k}_F)$, so the effective propagator can be written as

$$D(\omega, \mathbf{k}) = \frac{\omega_0^2}{\omega^2 - \omega_0^2 + i\delta}, \quad (31)$$

where $\sqrt{\omega_0^2 + c^2\mathbf{k}_F^2}$ is substituted by new effective frequency ω_0 . This approximation corresponds to the case of the optical phonon attraction (in the case when $\omega_0 \neq 0$). Generally speaking, the gap is frequency-dependent in this model. The problem of the crossover in the model with frequency dependent gap was studied in [32].

The system of the equations for the gap and for the chemical potential in this case is

$$\phi(\omega) = -ig^2 \int \frac{d^2k d\nu}{(2\pi)^2} \frac{\phi(\nu)}{\nu^2 - \xi(\mathbf{k})^2 - |\phi(\nu)|^2 + i\delta} \frac{\omega_0^2}{(\omega - \nu)^2 - \omega_0^2 + i\delta}, \quad (32)$$

$$2\epsilon_F = Re \int_0^\infty d\omega \left[\left(\frac{\omega}{\sqrt{\omega^2 - |\phi(\omega)|^2}} - 1 \right) \theta(\mu + \sqrt{\omega^2 - |\phi(\omega)|^2}) + \left(\frac{\omega}{\sqrt{\omega^2 - |\phi(\omega)|^2}} + 1 \right) \theta(\mu - \sqrt{\omega^2 - |\phi(\omega)|^2}) \right]. \quad (33)$$

Let us describe shortly how this system of the equations can be analyzed analytically. First of all, it is possible to show that the approximation $\phi(\omega) = \Delta = \text{const}$ in (33) is a rather good one. Then, this equation gives:

$$\mu = \epsilon_F - \frac{\Delta^2}{2\epsilon_F} \simeq \epsilon_F - \frac{|\varepsilon_b|}{2},$$

where the two-particle bound state energy ε_b depends on the coupling parameter in this case (see below).

After the Wick rotation $\omega \rightarrow i\omega$ the gap equation becomes

$$\phi(\omega) = g^2 \omega_0^2 \int \frac{d^2 k d\nu}{(2\pi)^3} \frac{\phi(\nu)}{\nu^2 + (\mathbf{k}^2/2m - \mu)^2 + \phi^2(\nu)} \frac{1}{(\omega - \nu)^2 + \omega_0^2}, \quad (34)$$

In polar coordinates, after integration over the angle we obtain:

$$\phi(\omega) = \frac{g^2 \omega_0^2}{(2\pi)^2} \int_{-\infty}^{+\infty} d\nu \frac{\phi(\nu)}{(\omega - \nu)^2 + \omega_0^2} \int_0^\infty \frac{k dk}{(k^2/2m - \mu)^2 + \nu^2 + \phi^2(\nu)}.$$

Since $\phi(\omega)$ is an even function of ω , it can depend only on ω^2 , we restrict the integration over ν to the positive values:

$$\phi(\omega) = \frac{\lambda \omega_0^2}{2} \int_0^\infty \frac{d\nu \phi(\nu)}{\sqrt{\nu^2 + \phi^2(\nu)}} \frac{1}{(\omega - \nu)^2 + \omega_0^2} \left[\frac{\pi}{2} + \arctan \frac{\mu}{\sqrt{\nu^2 + \phi^2(\nu)}} \right]. \quad (35)$$

The coupling constant $\lambda = g^2 m / (2\pi)$ is introduced. The asymptotic behavior for $\phi(\omega)$ is

$$\phi(\omega) \big|_{\omega \rightarrow \text{const}} \rightarrow 0, \quad \phi(\omega) \big|_{\omega \rightarrow \infty} \sim \frac{1}{\omega^2}. \quad (36)$$

We make the next replacement in the interaction potential [56, 57]:

$$\frac{1}{(\omega - \nu)^2 + \omega_0^2} = \frac{1}{\omega^2 + \omega_0^2} \theta(\omega - \nu) + \frac{1}{\nu^2 + \omega_0^2} \theta(\nu - \omega). \quad (37)$$

Then, the differentiation with respect to ω gives:

$$\phi'(\omega) = -\frac{\lambda \omega_0^2 \nu}{(\nu^2 + \omega_0^2)^2} \int_0^\omega \frac{d\nu \phi(\nu)}{\sqrt{\nu^2 + \phi^2(\nu)}} \left[1 + \frac{2}{\pi} \arctan \frac{\mu}{\sqrt{\nu^2 + \phi^2(\nu)}} \right], \quad (38)$$

It is evident that $\phi' < 0$, i.e. $\phi_{\max} = \phi(0) \equiv \Delta$.

Differentiating once more and introducing a new variable $x = \nu^2/\omega_0^2$ one gets the following differential equation

$$\begin{aligned} \phi''(x) + \frac{2}{x+1}\phi'(x) + \frac{\lambda}{4\sqrt{x}(x+1)^2\sqrt{x+(\phi(x)/\omega_0)^2}} \\ \times \left[1 + \frac{2}{\pi} \arctan \frac{\mu/\omega_0}{\sqrt{x+(\phi(x)/\omega_0)^2}} \right] \phi(x) = 0. \end{aligned} \quad (39)$$

with the boundary conditions

$$\phi'(x)|_{x=0} = 0; \quad [\phi(x) + (x+1)\phi'(x)]|_{x=\infty} = 0, \quad (40)$$

These conditions follow directly from (35), (37) and (38).

The analysis of this equation shows that the approximate solution for the gap in both weak and strong coupling regimes is (see [32] for details)

$$\Delta(\omega) \simeq \Delta\theta(\omega_0^2 - \omega^2),$$

where Δ is a parameter, which depends on the coupling and the carrier density, what is very important. In the weak coupling regime the parameter Δ has the following coupling and carrier density dependence:

$$\Delta = \sqrt{2|\varepsilon_b|\omega_0}\theta(\omega_0 - \epsilon_F) + \Delta_{BCS}\theta(\epsilon_F - \omega_0)$$

where $\Delta_{BCS} = 2\omega_0 e^{-1/\lambda}$ is the BCS expression for the gap and the bound state energy in this case is $\varepsilon_b = -2\omega_0 e^{-2/\lambda}$. In the strong coupling regime $\varepsilon_b \simeq \lambda$ and $\Delta_{BCS} \rightarrow (4/3)\lambda\omega_0$ at large carrier densities [31, 32].

To summarize, the crossover with carrier density and coupling changing in this effective model with retarded interaction is smooth and the gap is not small when the pair frequency is smaller than the boson frequency. This approach can be used for studying the crossover for the cases of different symmetries of the order parameter.

It is important to mention that the case considered here can be generalized on the case when one takes into account the vertex correction to the electron-phonon interaction. This correction is usually small when $\epsilon_F \gg \omega_0$ (the Migdal theorem). It was shown in [58], that this correction is also small when $\epsilon_F \ll \omega_0$. However, in some cases the vertex correction can lead to strong enhancement of superconductivity [36, 59, 60]. It is also necessary to note, that this correction even lead to enhancement of the *d*-wave superconductivity in the strongly correlated electron system [35, 36], despite phonon interaction due to the symmetry does not allow *d*-wave pairing in the case when the short range electron repulsion is not considered.

IV. FLUCTUATIONS

The role of fluctuations of the order parameter in the 2D and even in the 3D case at $T = 0$ can be significant. As it is shown in [19], the Gaussian fluctuation correction to the s -wave order parameter is non-negligible even in the weak-coupling case. It was shown that the fluctuations of the order parameter phase lead to increasing of the gap.

In this Section we show that the simultaneous order parameter modulus and phase fluctuations in the model with local attraction lead to strong increasing of the order parameter at small carrier densities and to small decreasing of the order parameter when the carrier densities are large.

At zero temperature the thermodynamic potential of the system with local attraction has the following form:

$$\Omega = v \left[\frac{|\Phi|^2}{V} - \int \frac{d^2k}{(2\pi)^2} (\sqrt{\xi^2(\mathbf{k}) + |\Phi|^2} - \xi(\mathbf{k})) \right].$$

In other words, it depends on the combination $|\Phi|^2 = (\Re\Phi)^2 + (\Im\Phi)^2$. For studying fluctuations of the OP, it is convenient to use new real variables:

$$\bar{\Phi}(x) = \begin{pmatrix} \phi_1(x) \\ \phi_2(x) \end{pmatrix},$$

such that $\bar{\Phi}^2(x) = \phi_1^2(x) + \phi_2^2(x) = |\Phi(x)|^2$. Another possibility is to choose the decomposition of the order parameter on its phase and modulus $\Phi(x) = \Delta(x) \exp(i\theta(x))$. However, it leads to some difficulties, since one needs to keep the order parameter modulus positive at functional integration over the fluctuations. The “old” order parameter variables are connected with the new ones in the following way:

$$\Phi(x) = \phi_1(x) + i\phi_2(x), \quad \Phi^*(x) = \phi_1(x) - i\phi_2(x).$$

We assume that the mean-field value of the field $\bar{\Phi}$ is chosen as

$$\bar{\Phi}_0(x) = \begin{pmatrix} \Delta \\ 0 \end{pmatrix}.$$

The order parameter $\bar{\Phi}$ can be written as

$$\bar{\Phi}(x) = \bar{\Phi}_0 + \delta\bar{\Phi}(x) \equiv \begin{pmatrix} \Delta + \delta\phi_1(x) \\ \delta\phi_2(x) \end{pmatrix} \quad (41)$$

in the case when its fluctuations are considered. We neglect the fluctuations of the carrier density $n_f(\mathbf{r})$, and consider the homogeneous constant value of n_f over the lattice $n_f(\mathbf{r}) = n_f = \text{const.}$

Substitution of (41) into the expression for the thermodynamic potential gives the following correction to the thermodynamic potential in the second order in the fluctuations [61]:

$$\delta\Omega = - \int_{-\infty}^{\infty} \frac{d\nu}{(2\pi)} \int \frac{d^2q}{(2\pi)^2} \delta\bar{\Phi}(i\nu, \mathbf{q}) \hat{A}(i\nu, \mathbf{q}) \delta\bar{\Phi}(-i\nu, -\mathbf{q}), \quad (42)$$

where $\hat{A}(i\nu, \mathbf{q}) = \frac{1}{V} + \chi(i\nu, \mathbf{q})$ is a 2×2 matrix with the susceptibility components

$$\chi_{jk}(i\nu, \mathbf{q}) = \frac{1}{2} \text{tr} \int_{-\infty}^{\infty} \frac{d\omega}{(2\pi)} \int \frac{d^2k}{(2\pi)^2} (-1)^{j+k} \mathcal{G}(i\omega_+, \mathbf{k}_+) \hat{\tau}_j \mathcal{G}(i\omega_-, \mathbf{k}_+) \hat{\tau}_k,$$

where $\omega_{\pm} = \omega \pm \nu/2$, $\mathbf{k}_{\pm} = \mathbf{p} \pm \mathbf{q}/2$. Integration over ω can be easily performed:

$$\begin{aligned} \chi_{11}(i\nu, \mathbf{q}) &= - \int \frac{d^2k}{(2\pi)^2} \frac{1}{2} \frac{E_+ + E_-}{\nu^2 + (E_+ + E_-)^2} \left[1 + \frac{\xi_+ \xi_- - \Delta^2}{E_+ E_-} \right], \\ \chi_{12}(i\nu, \mathbf{q}) &= -\chi_{21}(i\nu, \mathbf{q}) = - \int \frac{d^2k}{(2\pi)^2} \frac{1}{2} \frac{E_+ \xi_- + E_- \xi_+}{[\nu^2 + (E_+ + E_-)^2] E_+ E_-}, \\ \chi_{22}(i\nu, \mathbf{q}) &= - \int \frac{d^2k}{(2\pi)^2} \frac{1}{2} \frac{E_+ + E_-}{\nu^2 + (E_+ + E_-)^2} \left[1 + \frac{\xi_+ \xi_- + \Delta^2}{E_+ E_-} \right], \end{aligned}$$

where $E_{\pm} = \sqrt{\xi_{\pm}^2 + \Delta^2}$, $\xi_{\pm} = (\mathbf{k} \pm \mathbf{q}/2)^2/(2m) - \mu$ is the free fermion dispersion relation. After the integrating out of the fluctuation field $\bar{\Phi}$ the correction to thermodynamic potential has the next form

$$\delta\Omega = \frac{1}{2} \int_{-\infty}^{\infty} \frac{d\nu}{(2\pi)} \int \frac{d^2q}{(2\pi)^2} \ln \left[\left\{ \frac{1}{V} + \chi_{11}(i\nu, \mathbf{q}) \right\} \left\{ \frac{1}{V} + \chi_{22}(i\nu, \mathbf{q}) \right\} - \chi_{12}(i\nu, \mathbf{q}) \chi_{21}(i\nu, \mathbf{q}) \right].$$

The factor $\sim \Delta$ which appears in the measure of functional integration over Δ in Z due to taking into account the symmetry of the thermodynamic potential with respect to the transformation $\bar{\Phi} \rightarrow e^{i\alpha} \bar{\Phi}$ (see, for example [61]) is omitted in the last expression. This factor can be absorbed in the measure of the functional integral over Δ in the partition function, where the functional integration can be actually performed over the variable Δ^2 . Let us note, that only the first component $(\frac{1}{V} + \chi_{11}(i\nu, \mathbf{q}))$ under the logarithm in $\delta\Omega$ will be present when one considers the particular case of the order parameter phase fluctuations.

It is useful to diagonalize the matrix $\hat{A}$, to find the contributions which come from the phase and the modulus fluctuations of the order parameter. Obviously, the first component

will correspond to the phase fluctuations and the second - for the modulus fluctuations, as it follows from the definitions of the field $\bar{\Phi}$. So, it is easy to arrive to the following representation

$$\delta\Omega = \frac{1}{2} \int_{-\infty}^{\infty} \frac{d\nu}{(2\pi)} \int \frac{d^2q}{(2\pi)^2} \ln \left[\left\{ \frac{1}{V} + \chi_{\theta}(i\nu, \mathbf{q}) \right\} \left\{ \frac{1}{V} + \chi_{\Delta}(i\nu, \mathbf{q}) \right\} \right],$$

where

$$\chi_{\theta}(i\nu, \mathbf{q}) = \frac{1}{2} [\chi_{11}(i\nu, \mathbf{q}) + \chi_{22}(i\nu, \mathbf{q})] - \sqrt{\frac{1}{4} [\chi_{11}(i\nu, \mathbf{q}) - \chi_{22}(i\nu, \mathbf{q})]^2 - \chi_{12}(i\nu, \mathbf{q})\chi_{21}(i\nu, \mathbf{q})}$$

$$\chi_{\Delta}(i\nu, \mathbf{q}) = \frac{1}{2} [\chi_{11}(i\nu, \mathbf{q}) + \chi_{22}(i\nu, \mathbf{q})] + \sqrt{\frac{1}{4} [\chi_{11}(i\nu, \mathbf{q}) - \chi_{22}(i\nu, \mathbf{q})]^2 - \chi_{12}(i\nu, \mathbf{q})\chi_{21}(i\nu, \mathbf{q})}$$

are the effective contributions to the thermodynamic potential from the fluctuations of the order parameter phase and the modulus, correspondingly.

The equations for the gap and for the chemical potential (25) and (10) have the next form in the case of the Gaussian correction to the thermodynamic potential due to the order parameter fluctuations:

$$\begin{aligned} \frac{\Delta}{V} &= \int \frac{d^2q}{(2\pi)^2} \frac{\Delta}{2\sqrt{\xi(\mathbf{q})^2 + \Delta^2}} + \frac{1}{2} \int_{-\infty}^{\infty} \frac{d\nu}{(2\pi)} \int \frac{d^2q}{(2\pi)^2} \left[\frac{\partial\chi_{\theta}(i\nu, \mathbf{q})/\partial\Delta}{1/V + \chi_{\theta}(i\nu, \mathbf{q})} + \frac{\partial\chi_{\Delta}(i\nu, \mathbf{q})/\partial\Delta}{1/V + \chi_{\Delta}(i\nu, \mathbf{q})} \right], \\ n_f &= \int \frac{d^2q}{(2\pi)^2} \left[1 - \frac{\xi(\mathbf{q})}{\sqrt{\xi(\mathbf{q})^2 + \Delta^2}} \right] + \int_{-\infty}^{\infty} \frac{d\nu}{(2\pi)} \int \frac{d^2q}{(2\pi)^2} \left[\frac{\partial\chi_{\theta}(i\nu, \mathbf{q})/\partial\mu}{1/V + \chi_{\theta}(i\nu, \mathbf{q})} + \frac{\partial\chi_{\Delta}(i\nu, \mathbf{q})/\partial\mu}{1/V + \chi_{\Delta}(i\nu, \mathbf{q})} \right]. \end{aligned}$$

Considering the limit of weak coupling, the functions χ_{θ} and χ_{Δ} in the denominators can be neglected, than the integration over ν can be performed and after some trivial manipulations the following simple equation can be obtained:

$$\frac{1}{V} = \int \frac{d\mathbf{q}}{(2\pi)^2} \frac{1}{2\sqrt{\xi^2(\mathbf{q}) + \Delta^2}} + \frac{V}{2} \int \frac{d^2k}{(2\pi)^2} \int \frac{d^2q}{(2\pi)^2} \frac{\xi_+ \xi_-}{E_+^3 E_-}, \quad (43)$$

$$n_f = \int \frac{d\mathbf{q}}{(2\pi)^2} \left[1 - \frac{\xi(\mathbf{q})}{\sqrt{\xi^2(\mathbf{q}) + \Delta^2}} \right] + V \int \frac{d^2k}{(2\pi)^2} \int \frac{d^2q}{(2\pi)^2} \frac{\Delta^2(\xi_+ - \xi_-)}{E_+^3 E_-} \quad (44)$$

(compare with (17) and (18)). The substitution $\mathbf{q} \rightarrow -\mathbf{q}$ in a part of the terms was made in obtaining equations (43) and (44). It is interesting to note that in the case of the phase fluctuations the numerator under integral in the last term of the the gap equation will be $\frac{1}{2}\xi_+(\xi_- - \xi_+)$ and the last term in the number equation will be multiplied by $\frac{1}{2}$. It is also a good approximation to put $\mu = \epsilon_F$, since in the weak coupling regime μ is different from ϵ_F

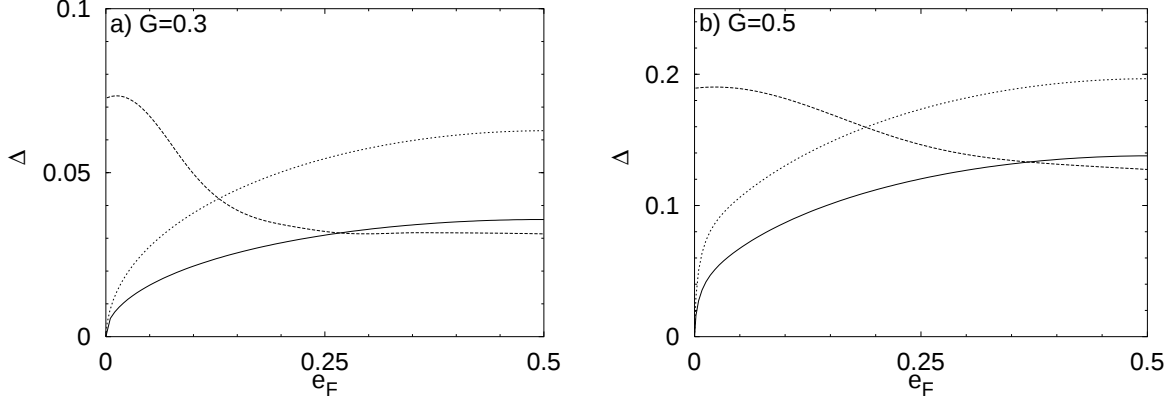


FIG. 6: The dependence of Δ on ϵ_F is presented for the mean-field solution case (solid line) and for the order parameter fluctuations case (dashed line) at different values of the dimensionless coupling parameter $G = mV/(2\pi)$. The dotted line is the estimation of Koř and Millis [19] for the case of the order parameter phase fluctuations.

only at very low carried densities. The solution of the equation (43) for the gap parameter as function of ϵ_F at $\mu = \epsilon_F$ and different values of the coupling constant is presented in Fig. 6. The estimation of the order parameter in the case of phase fluctuation is also presented. As it was shown in [19] in the 2D case the phase fluctuations lead to an effective increasing of the coupling constant $V \rightarrow V(1 + \frac{2}{\pi^2})$. The gap can be calculated from the standard mean-field BCS equation. The comparison of different cases shows that the phase fluctuations lead to the gap increasing, while the total fluctuations lead to much stronger increasing of the gap at small carrier densities and to decreasing of the gap when the carrier density is large. The last result is familiar, but the first one is very surprising. The dependence of the gap on coupling at a small value of the carrier density is presented in Fig.7. These results suggest that the higher order corrections in fluctuations should be studied to better understand the behavior of the system.

It should be mentioned that the role of the disorder due dopants in the fluctuations of the inhomogeneous order parameter was studied by Yu.G. Pogorelov and by the authors in [62, 63, 64]. We don't describe this important problem here, since it deserves a special review.

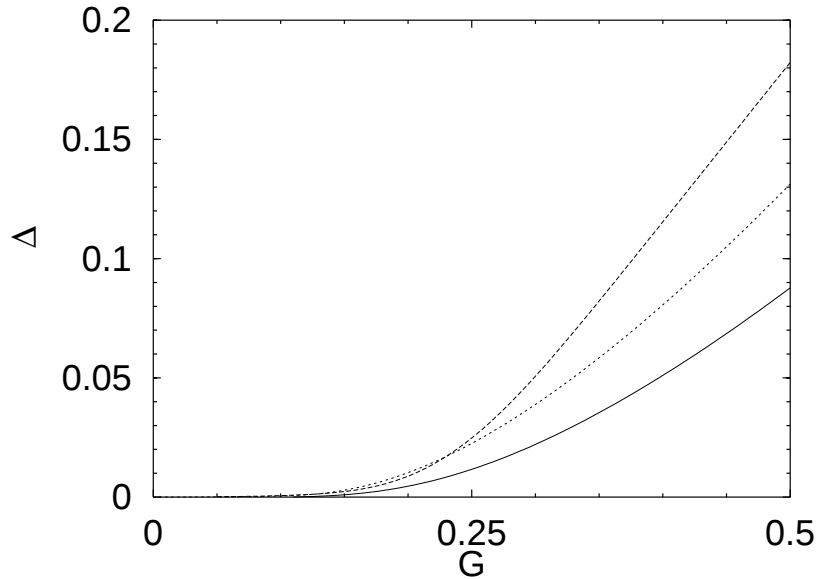


FIG. 7: The dependence of Δ on G is presented for mean field solution case (solid line) and for order parameter fluctuations case (dashed line) at $\epsilon_F = 0.1$. The dotted line is the estimation from [19] for the order parameter phase fluctuations.

V. CONCLUSIONS

In this paper the crossover from superfluidity to superconductivity with doping increasing at $T = 0$ in the cases of the s -wave and d -wave pairing was reviewed. In the 3D case this crossover does not take place at small couplings, and the same situation takes place in the d -wave pairing case in two-dimensions, when the interaction does not depend on the doping. In the case when the correlation radius depends on doping the minimal value of coupling for the two-particle bound state exists even in the s -wave channel. Also the gap can decrease with the doping in this case.

It was also shown, that the fluctuations of the order parameter play an important role at $T = 0$. The fluctuations of the order parameter phase in weak coupling limit in the case of the s -wave pairing regime lead to increasing of superconductivity at any physical carrier density, while the modulus fluctuations lead to much stronger increasing of superconductivity at small carrier densities, while at large carrier densities they lead to suppression of the order parameter, as a result the gap is decreasing in BCS regime, when both the modulus and the phase fluctuations are taken into account. This means that the higher order fluctuation corrections must be investigated in order to understand the self-consistent theory at low

carrier densities.

We would like to mention some direction which can be interesting for the future investigations. Studying of the problem of the crossover with realistic dispersion relations is not performed even on the mean-field level in many interesting cases. The interplay between disorder and superconductivity, and strong correlation and superconductivity is another interesting topic for the investigations.

The fluctuations in the d -wave pairing channel and in other non-isotropic pairing channels even in the case of Gaussian fluctuations were not studied carefully so far. It is also important to go beyond the Gaussian fluctuations, since the pair susceptibility is diverging in the 2D and in the 3D cases, as it was mentioned in Ref.[19]. The role of the inter-layer coupling is another problem which is not solved in general at the moment. The solution of the problem mentioned above will lead to better understanding of the superconducting properties of systems with arbitrary carrier density and pairing potential.

Acknowledgments

V.M.L. acknowledges partial support by SCOPES-project 7UKPJ062150.00/1 of the Swiss National Science Foundation.

-
- [1] D.M. Eagles, Phys. Rev. **186**, 456 (1969).
 - [2] H.P.R. Frederikse, Phys. Rev. Lett. **16**, 579 (1966).
 - [3] R.A. Ogg, Jr., Phys. Rev. **69**, 243 (1946).
 - [4] M.R. Schafroth, Phys. Rev. **96**, 1149 (1954).
 - [5] M.R. Schafroth, Phys. Rev. **96**, 1442 (1954).
 - [6] M.R. Schafroth, Phys. Rev. **100**, 463 (1955).
 - [7] A.J. Leggett, in *Modern Trends in The Theory of Condensed Matter* (Springer-Verlag, 1980), P.13.
 - [8] P. Nozières and P. Schmitt-Rink, J. Low Temp. Phys. **59**, 195 (1985).
 - [9] R. Micnas, J. Ranninger, and S. Robaszkiewicz, Rev. Mod. Phys. **62**, 113 (1990).
 - [10] C.A.R. Sá de Melo, M. Randeria, and J.R. Engelbrecht, Phys. Rev. Lett. **71**, 3202 (1993).

- [11] R. Haussmann, Phys. Rev. B **49**, 12975 (1994).
- [12] M. Randeria, in: A. Griffin, D.W. Snoke, and S. Stringari (Eds.), *Bose-Einstein Condensation* (Cambridge U.P., New York, 1995), P.355.
- [13] J.R. Engelbrecht, M. Randeria, C.A.R. Sá de Melo, Phys. Rev. B **55**, 15153 (1997).
- [14] M. Marini, F. Pistolesi, and G.C. Strinati, Eur. J. Phys. B **1**, 151 (1998).
- [15] N. Andrenacci, A. Perali, P. Pieri, and G.C. Strinati, Phys. Rev. B **60**, 12410 (1999).
- [16] E. Babaev, Phys. Rev. B **63**, 184514 (2000).
- [17] F. Pistolesi, G.C. Strinati, Phys. Rev. B **53**, 15168 (1996).
- [18] I.J.R. Aitchison, P. Ao, D.J. Thouless, and X.-M. Zhu, Phys. Rev. B **51**, 6531 (1995).
- [19] S. Koš, A.J. Millis, preprint cond-mat/0207190 (2002).
- [20] E.V. Gorbar, V.M. Loktev, and S.G. Sharapov, Physica C **257**, 355 (1996).
- [21] N.D. Mermin, H. Wagner, Phys. Rev. Lett. **17**, 1113 (1966); P.C. Hohenberg, Phys. Rev. **158**, 383 (1967); S. Coleman, Comm. Math. Phys. **31**, 259 (1973).
- [22] M. Randeria, J.-M. Duan, and L.Y. Sheih, Phys. Rev. Lett. **62**, 981 (1989).
- [23] M. Randeria, J.-M. Duan, and L.Y. Sheih, Phys. Rev. B **41**, 327 (1990).
- [24] F. Pistolesi, G.C. Strinati, Phys. Rev. B **49**, 6356 (1994).
- [25] R. Fehrenbacher and M.R. Norman, Phys. Rev. Lett. **74**, 3884 (1995).
- [26] P. Nozières and F. Pistolesi, Eur. Phys. J. B **10**, 649 (1999).
- [27] E.V. Gorbar, V.P. Gusynin, and V.M. Loktev, Sov. Low. Temp. Phys. **19**, 832 (1993).
- [28] L.S. Borkowski and C.A.R. Sá de Melo, preprint cond-mat/9810370 (1998).
- [29] R.D. Duncan and C.A.R. Sá de Melo, Phys. Rev. B **62**, 9675 (2000).
- [30] M. Capone, C. Castellani, and M. Grilli, Phys. Rev. Lett. **88**, 126403 (2002).
- [31] V.M. Loktev, V.M. Turkowski, S.G. Sharapov, Journ. of Phys. Studies (Ukraine) **1**, 431 (1997) (in Ukrainian).
- [32] V.M. Loktev, V.M. Turkowski, S.G. Sharapov, Teor. i Mat. Fiz. **115**, 419 (1998) (English transl.: Teor. and Math. Phys. **115**, 694 (1998)).
- [33] B.C. den Hertog, Phys. Rev. B **60**, 559 (1999).
- [34] S. Stintzing and W. Zwerger, Phys. Rev. B **56**, 9004 (1997).
- [35] M. Mierzejewski, J. Zieliński, P. Entel, Phys. Rev. B **57**, 590 (1998).
- [36] P. Paci, C. Grimaldi, and L. Pietronero, Eur. Phys. J. B **17**, 235 (1999).
- [37] K.A. Musaelian, J. Betouras, A.V. Chubukov, and R. Joynt, Phys. Rev. B **53**, 3598 (1996).

- [38] E.V. Gorbar, V.M. Loktev, and V.S. Nikolaev, Supercond. Phys. Chem. Techn. **7**, 1 (1994).
- [39] J.P. Wallington and J.F. Annett, Phys. Rev. B **61**, 1433 (2000).
- [40] M.B. Soares, F. Kokubun, J.J. Rodríguez-Núñez and O. Rendón, Phys. Rev. B **65**, 174506 (2002).
- [41] A. Perali, P. Pieri, G.C. Strinati, preprint cond-mat/0211132 (2002).
- [42] F. Pistolesi, Ph. Nozières, Phys. Rev. B **66**, 054501 (2002).
- [43] V.M. Loktev and V. Turkowski, Physica C **383**, 256 (2002).
- [44] J. Batle, M. Casas, M. Fortes et al, preprint cond-mat/0211456 (2002).
- [45] C.C. Tsuei and J. R. Kirtley, Rev. Mod. Phys. **72**, 969 (2000).
- [46] J.A. Skinta, T.R. Lemberger, T. Greibe and M. Naito, Phys. Rev. Lett. **87**, 207003 (2002).
- [47] C.-T. Chen, P. Seneor, N.-C. Yeh et al, Phys. Rev. Lett. **88**, 227002 (2002).
- [48] G.-m. Zhao, Phys. Rev. B **64**, 024503 (2002).
- [49] N.-C. Yeh, C.-T. Chen, G. Hammerl et al, Phys. Rev. Lett. **87**, 087003 (2001).
- [50] A. Biswas, P. Fournier, M.M. Qazilbash et al, Phys. Rev. Lett. **88**, 207004 (2002).
- [51] J.A. Skinta, M-S. Kim, and T.R. Lemberger et al, Phys. Rev. Lett. **88**, 207005 (2002).
- [52] C. Proust, E. Boaknin, R.W. Hill et al, Phys. Rev. Lett. **89**, 147003 (2002).
- [53] H. Kleinert, Fortschr. Phys. **26**, 565 (1978).
- [54] T.R. Thurston, R.J. Birgeneau, M.A. Kastner et al, Phys. Rev. B **40**, 4585 (1989).
- [55] A.L. Fetter, J.D. Walecka, *Quantum Theory of Many-Particle Systems*, McGraw-Hill, New York (1971).
- [56] T. Appelquist, M.J. Bowick, D. Karabali, L.C.R. Wijewardhana, Phys. Rev. D. **33**, 3774 (1986).
- [57] V.P. Gusynin, V.A. Miransky, I.A. Shovkovy, Nucl. Phys. B **462**, 249 (1996).
- [58] M.A. Ikeda, A. Ogasawara, and M. Sugihara, Phys.Lett. A **170**, 319 (1992).
- [59] L. Pietronero, S. Strassler, Europhys. Lett. **18**, 627 (1992).
- [60] C. Grimaldi, L. Pietronero, S. Strassler, Phys. Rev. Lett. **75**, 1158 (1995).
- [61] J. Negele and H. Orland, "Quantum Many-Particle Systems", Addison-Wesley (1987).
- [62] V.M. Loktev, Yu.G. Pogorelov, Physica C **272**, 151 (1996).
- [63] V.M. Loktev, Yu.G. Pogorelov, Low. Temp. Phys. **27**, 1039 (2001).
- [64] V.M. Loktev, Yu.G. Pogorelov, V.M. Turkowski, preprint cond-mat/0302310 (2003); to be published in Int. Journ. of Mod. Phys. B.